IEC 62047-43

Edition 1.0 2024-03

INTERNATIONAL STANDARD

colour inside

Semiconductor devices – Micro-electromechanical devices – Part 43: Test method of electrical characteristics after cyclic bending deformation for flexible micro-electromechanical devices



IEC 62047-43:2024-03(en)

THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembé
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC
The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications
The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform
The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, …). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished
Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc
If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch
Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org
The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC 62047-43

Edition 1.0 2024-03

INTERNATIONAL STANDARD

colour inside

Semiconductor devices – Micro-electromechanical devices – Part 43: Test method of electrical characteristics after cyclic bending deformation for flexible micro-electromechanical devices

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 31.080.99

ISBN 978-2-8322-8498-8

Warning! Make sure that you obtained this publication from an authorized distributor.

® Registered trademark of the International Electrotechnical Commission

CONTENTS

FOREWORD 3
INTRODUCTION 5
1 Scope 6
2 Normative references 6
3 Terms and definitions 6
4 Test piece 7
4.1 General 7
4.2 Shape of a test piece 7
5 Test method 9
5.1 Principle 9
5.2 Test apparatus and instrumentation 10
5.2.1 Test apparatus 10
5.2.2 Instrumentation 10
5.3 Procedure 11
5.3.1 Testing conditions 11
5.3.2 Selection of bending direction 11
5.3.3 Determination of bending axes 12
5.3.4 Measurement of test piece dimensions 12
5.3.5 Measurement of folding distance 12
5.3.6 Number of testing 12
5.3.7 Instrumentation 13
5.3.8 End of testing 13
6 Test report 13
6.1 General 13
6.2 Bending direction(s) and in-plane locations of bending axes 13
6.3 Dimensions of the test piece 13
6.4 Performance degradation characteristics with the folding distance 14
6.5 Testing conditions 14
Annex A (informative) Example of P-S-N plot of flexible MEMS device 16

Figure 1 – Schematic explanation of cyclic bending test 7
Figure 2 – Schematic illustration of flexible MEMS test piece 8
Figure 3 – Selection of bending axis 9
Figure 4 – Folding procedures 10
Figure 5 – 3-dimensional P-S-N plot 14
Figure A.1 – Test piece – Printed wiring on paper substrate 17
Figure A.2 – Test apparatus 17
Figure A.3 – 3-dimensional P-S-N plot 18
Figure A.4 – 2-dimensional P-S-N plot 18

INTERNATIONAL ELECTROTECHNICAL COMMISSION

_____

SEMICONDUCTOR DEVICES – MICRO-ELECTROMECHANICAL DEVICES –

Part 43: Test method of electrical characteristics after cyclic bending deformation for flexible micro-electromechanical devices

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at https://patents.iec.ch. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 62047-43 has been prepared by subcommittee 47F: Micro-electromechanical devices, of IEC technical committee 47: Semiconductor devices. It is an International Standard.

The text of this International Standard is based on the following documents:

Draft	Report on voting
47F/459/FDIS	47F/464/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 62047 series, published under the general title *Semiconductor devices – Micro-electromechanical devices*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

In the recent trend toward ubiquitous sensor society and the world of internet of things, demand and thus the market for softer electronic devices are quickly expanding. That is what flexible micro-electromechanical devices are for, some of which are already released into the market. Even a so-called foldable device is under development and will soon appear in the market. However, to operate trillions of such devices for the comfort and safety of human beings, the reliability of the individual devices is a critical concern. Especially in the case of flexible devices, robustness against bending deformation is an important issue which will be shared among all the producers and users of such devices. In addition, since such devices are bent usually not only once but some numbers of cycles, information on performance deterioration along with the number of cycles is also important.

In order to understand how safe a situation is, even after numbers of cycles, performance deterioration behaviour of those devices as a function of loading levels and cycles needs to be evaluated so as to ensure secure operation during expected service periods. This standard procedure of testing is designed with the emphasis on such points and with the applicability not only to already emerging flexible devices but also to so-called foldable devices which still function even when the device is folded.

SEMICONDUCTOR DEVICES – MICRO-ELECTROMECHANICAL DEVICES –

Part 43: Test method of electrical characteristics after cyclic bending deformation for flexible micro-electromechanical devices

1 Scope

This part of IEC 62047 specifies the test method of electrical characteristics after cyclic bending deformation for flexible electromechanical devices. These devices include passive micro components and active micro components on the flexible film or embedded in the flexible film. The desired in-plane dimensions of the device for the test method ranges typically from 1 mm to 300 mm and the thickness ranges from 10 µm to 1 mm, but these are not limiting values. The test method is so designed as to understand and further visualize the entire performance deterioration behaviour after cyclic bending deformation in a concept of 3D (P-S-N: Performance – Severity of bending – Number of cycles) plot over the loading space of severity of bending and number of repeated cycles. This document is essential to estimate safety margin over the operation period under a certain level of cyclic bending deformation and indispensable for reliable design of the product employing these devices.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62047-35:2019, *Semiconductor devices – Micro-electromechanical devices – Part 35: Test method of electrical characteristics under bending deformation for flexible electro-mechanical devices*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at https://www.electropedia.org/
- ISO Online browsing platform: available at https://www.iso.org/obp


3.1
d_{max}
maximum folding distance
maximum distance between two loading walls, representing severity of bending, i.e. loading level, applied to the device, as indicated in Figure 1

3.2
d_{min}
minimum folding distance
minimum distance between two loading walls, representing severity of bending, i.e. loading level, applied to the device, as indicated in Figure 1

Note 1 to entry: The degree of bending given to the device is here represented by the distance between two walls approaching close to each other to bend the device, which is denoted as folding distance.

Note 2 to entry: This measure may be optionally converted to the radius of curvature *r* and also converted to the bending strain ε given around a bending axis. The strain is one of the suitable parameters for estimating the damage of materials through cyclic mechanical loading. But here it may not be uniform between the two walls especially when the rigidity distribution around the bending axis is not homogeneous due to the heterogeneity of structures. The nominal value of the radius is proportional to the distance, and the bending strain is in inverse proportion to the radius. Thus, the maximum of nominal bending strain occurs at the minimum folding distance.

3.3
shuttle range
travel distance of moving wall, as indicated in Figure 1

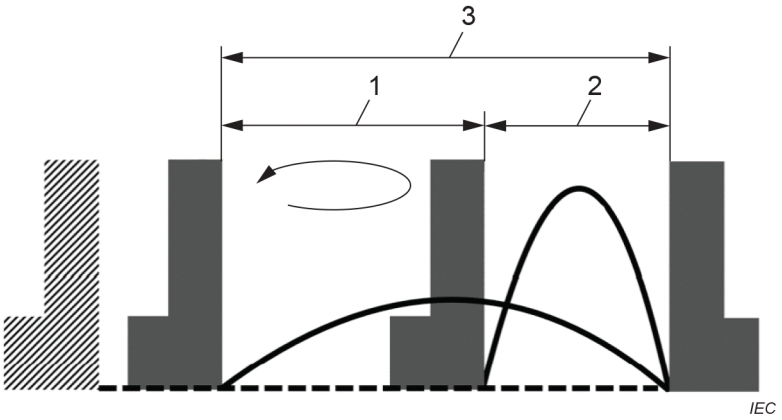

1 shuttle range

2 minimum folding distance

3 maximum folding distance

Figure 1 – Schematic explanation of cyclic bending test

4 Test piece

4.1 General

Flexible MEMS device, which is bent in use, can be in principle a test piece as it is and subjected to the evaluation of this document. In principle, this test-method is applicable without restriction on size and shape of devices. However, for the ease of load application, it may be cut into a rectangular shape with target parts to be loaded at the centre as mentioned in 4.2.

4.2 Shape of a test piece

A rectangular shape of test piece should be used for the ease of experiment as shown in Figure 2. It can be necessary to cut out a part of devices for the test, especially when the target part to be tested, which determines its own functional feature, is not located in the centre of the device. In this case, the test piece shall be prepared in a rectangular form by cutting a part out of the entire device with the target part located at the centre of two parallel edges which should also be parallel to the bending axis. This is because the point to be loaded to the end is limited in this test method only along the bending axis likely coming out at the centre due to the loading scheme explained in 5.1.