INTERNATIONAL STANDARD

ISO 14322

Second edition
2018-07

Plastics — Epoxy resins — Determination of degree of crosslinking of crosslinked epoxy resins by differential scanning calorimetry (DSC)

Plastiques — Résines époxydes — Détermination du degré de réticulation des résines époxydes réticulées par analyse calorimétrique différentielle (DSC)

Reference number
ISO 14322:2018(E)

© ISO 2018



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

 © ISO 2018 – All rights reserved

Contents

Page

Foreword ..... **iv**
Introduction ..... **v**
1 Scope **1**
2 Normative references **1**
3 Terms and definitions **1**
4 Principle **2**
5 Materials **3**
6 Apparatus **3**
7 Procedure **3**
7.1 Calibration 3
7.2 Preliminary test 4
7.2.1 General 4
7.2.2 Procedure for preliminary test 4
7.3 DSC measurement on the crosslinked resin under investigation 4
8 Expression of results **5**
9 Precision **5**
9.1 General 5
9.2 Materials and crosslinking conditions 5
9.3 Precision of the method 5
10 Test report **6**
Annex A (informative) **Example of a procedure used for the preliminary test, with typical operating conditions** **7**
Bibliography **8**

© ISO 2018 – All rights reserved

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 12, *Thermosetting materials*.

This second edition cancels and replaces the first edition (ISO 14322:2012), of which it constitutes a minor revision.

The changes compared to the previous edition are as follows:

— the title has been updated (DSC has been added at the end);

— Clause 2 has been updated;

— the subclauses under 7.2 have been renumbered;

— editorial changes have been applied.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

© ISO 2018 – All rights reserved

Introduction

It is possible to determine the degree of crosslinking of a crosslinked epoxy resin by observing changes in its mechanical, electrical or thermal properties.

However, such an approach is inadequate in cases in which the test sample is to be evaluated as is or is to be examined under various crosslinking conditions. This document provides a method whereby the degree of crosslinking is determined without the need for complicated procedures for preparing, conditioning or configuring the test sample. The degree of crosslinking is determined by comparing the heat of the crosslinking reaction for the test sample with that of a reference sample, using a differential scanning calorimeter.

The advantages of this method are that sample preparation is simple and measurements can be made with very small amounts of sample. For these reasons, this document is useful for investigations of, and in establishing conditions for, crosslinking reactions. It can also be used for production and quality control.

Finally, since epoxy resin systems are highly diverse, the applicability of this document to each resin system needs be established. A technique to test the applicability to an epoxy resin system is included in this document.

© ISO 2018 – All rights reserved

Plastics — Epoxy resins — Determination of degree of crosslinking of crosslinked epoxy resins by differential scanning calorimetry (DSC)

SAFETY STATEMENT — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to determine the applicability of any other restrictions.

1 Scope

This document specifies a method whereby the heat of reaction generated during epoxy resin crosslinking is measured by differential scanning calorimetry (DSC). The degree of crosslinking is determined based on this result.

This method is applicable to epoxy resin systems with a moderate or slow crosslinking-reaction speed. It might not be applicable to systems with a fast crosslinking-reaction speed at ambient temperature.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this documents. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 11357-1, *Plastics — Differential scanning calorimetry (DSC) — Part 1: General principles*

ISO 11409, *Plastics — Phenolic resins — Determination of heats and temperatures of reaction by differential scanning calorimetry*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11357-1 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at https://www.iso.org/obp

— IEC Electropedia: available at http://www.electropedia.org/

3.1
degree of crosslinking
value which indicates the extent of the crosslinking reaction of an epoxy resin system

Note 1 to entry: The degree of crosslinking is expressed as a percentage and calculated in accordance with Formula (2).

3.2
uncrosslinked epoxy resin system
epoxy resin system immediately after mixing the system components, before any crosslinking has taken place

© ISO 2018 – All rights reserved

3.3
total heat of reaction
gross amount of reaction heat produced by an *uncrosslinked epoxy resin system* (3.2) during complete crosslinking, as determined by DSC

Note 1 to entry: It is expressed in joules per gram ($J \cdot g^{-1}$).


4 Principle

The total heat of reaction is first measured by DSC, using a test sample taken from the uncrosslinked epoxy resin system. Curve A in Figure 1 is an example of such a DSC curve.

The heat of reaction of a test sample of the (partly) crosslinked resin system under investigation is then measured, using the same DSC apparatus and under the same conditions as those used to measure the total heat of reaction, in order to determine the heat of reaction due to the remaining reactive groups as the reaction goes to completion. Curves B1 and B2 in Figure 1 are examples of DSC curves obtained with such test samples.

Curve B1 shows a case where crosslinking did not progress to a large extent before the DSC measurement and curve B2 shows a case where crosslinking progressed considerably before the DSC measurement.

The degree of crosslinking of the (partly) crosslinked resin system is determined from the heat of reaction of this crosslinked resin system and the total heat of reaction of the uncrosslinked resin system [see Formula (2)].

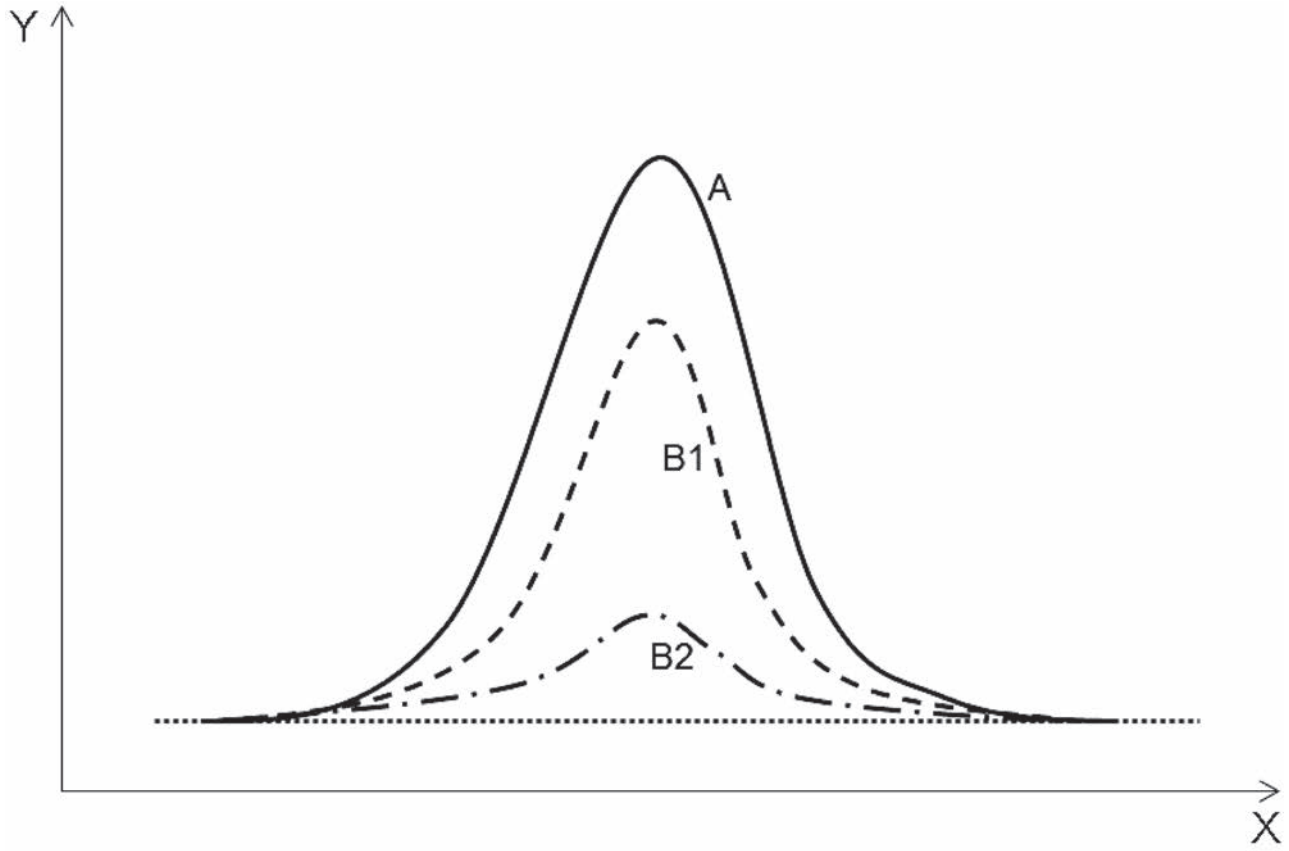

Key
X temperature or time
Y heat flow rate (exothermic)

Figure 1 — DSC curve (schematic)

© ISO 2018 – All rights reserved